

# **The Efficacy of Graphene oxide and Reduced Graphene oxide with Metal oxides for photodegradation of dyes**

M. Beaula Ruby Kamalam, S. Ashok Kumar and S. S. R. Inbanathan

Post Graduate and Research Department of Physics, The American College, Madurai-625002, Tamilnadu, India

## **Abstract**

The use of photocatalyst for the destruction of synthetic and organic pollutants, such as dyes and chemicals, has developed as a successful method for the treatment of wastewater. In this study, we have mainly focused on two-dimensional graphene oxide (GO) and reduced graphene oxide (rGO), which have high oxygen functionality, sizable surface areas, and effective adsorption sites, as photocatalytic materials. The GO/rGO composites outperform electron-hole pairs recombination rate and minimize energy gaps, enhancing the photodegradation performance of metal oxide composites. This is accomplished by changing the level of the valence band and conduction band.

## **Introduction**

Colored organic compounds are frequently discarded in wastewater at the end of the production process in a number of industrial operations, including textile, food, tannery, paper, printing, and cosmetics. These dyes affect the aquatic ecosystem by coloring the water and blocking light from penetrating, which reduces photosynthesis and lowers the amount of dissolved oxygen in the water. Additionally, this kind of pollutant may have genotoxic impacts on fauna, flora, and human health in addition to having carcinogenic, hypersensitive, and other negative effects [1-5]. Dyes are synthetic organic molecules, including azo, sulfur, nitro, triphenylmethane, acidic, and basic ones. The industries of leather, textiles, and biology all benefit from the usage of brilliant green (BG), a dye based on triphenylmethane. However, drinking water tainted with BG can harm people and result in hypertension, heart, lung, and kidney problems, as well as cancer that can be passed onto future generations [6-12]. Methylene blue (MB) can induce eye burns in both people and animals, which is one of its many major negative effects. When consumed, MB stimulates the digestive system and causes nausea, vomiting, and diarrhoea. In addition, it can cause convulsions, cyanosis, methemoglobinemia, dyspepsia, and tachycardia. To maintain ecological balance, it is crucial to remove dye from contaminated water due to the negative effects on people, animals, and

aquatic life [13-15]. Adsorption, ion change, membrane separation, chemical precipitation, photocatalytic method, and other techniques have all been developed in the field of wastewater treatment. [16].

In this regard, the environmentally friendly and cost-effective way of removing the dye from water bodies is photodegradation of the dye under the stimulation of light [17]. The design and prospective uses of nanostructured semiconductor materials for energy, the environment, and water sanitization have recently been examined. However, before the photocatalysts are commercially feasible for extensive industrial applications, a number of basic difficulties need to be resolved. Due to their ability to break down organic dyes when exposed to light, these semiconductor photocatalysts are among the most promising photocatalysts and offer an affordable and simple method for water filtration. On the photocatalyst surface, electron-hole pairs are produced as a result of light absorption during the photocatalytic reaction. Charge carriers produced by photosynthesis migrate toward the catalyst surface and produce reactive oxygen species (ROS) [18-21]. Finally, these ROS degrade the dye molecule present. For instance, the fast recombination of electron-hole pairs (EHPs) and the discrepancy between the band gap energy and the solar radiation spectrum limit the use of metal oxide photocatalysts. Due to the large band gap of the photocatalysts ( $\sim > 3$  eV), the photocatalyst must be activated by UV light, which significantly limits the technology's use in practical applications. [22-24]. At the moment, there is a lot of focus on creating composite systems and heterostructures based on semiconductors for visible light driven photocatalysis. The practical limitations on their photocatalytic capabilities, however, include low visible light absorption, a wide band gap energy, and rapid EHPs recombination. As a result, the design and development of semiconductor nanocomposite (NC) materials has recently become a very promising field of study.

Designing GO semiconductor composites has received particular attention in an effort to boost the photocatalytic performance of the photocatalyst, notably for water remediation. Graphite oxide sheet, often known as GO, is the end result of the chemical exfoliation of graphite. It is a 2D material made up of an atom-thick  $sp^2$  carbon network. With its exceptional mechanical properties, huge theoretical surface area ( $2630\text{m}^2/\text{g}$ ), high transparency, and distinctive two-dimensional long-range conjugation structure, graphene makes an excellent platform for the grafting of various semiconductor materials. It also makes it possible for the transfer of photogenerated charge carriers, which is made possible by its magnificent electrical and thermal conductivity, as well as its assorted derivatives with enchanting surface properties

[25-30]. Semiconductor materials may be adhered to the surface of GO, where photogenerated electrons are then transferred, enhancing the photocatalytic degradation efficiency. Because of its distinctive characteristics, such as ease of synthesis, vast surface area, layered structure, and excellent thermal and chemical durability, GO is a significant member of the carbon family [31-35]. Due to its exceptional qualities, GO is widely employed in a variety of applications, including bio-applications, sensors, photovoltaics, energy and electronic devices, catalysis, and more. Because of its hydrophilic characteristics and the abundant oxygen groups on its basal and edge surfaces, GO has the advantage of being able to interact with and absorb organic compounds and dyes in water treatment applications. In addition to interacting with water and other polar solvents, functional groups like epoxy, hydroxyl, and carboxyl groups also exhibit  $\pi$ - $\pi$  stacking interactions [36-43]. In addition, it is simple to reduce these functional groups to generate rGO. Furthermore, these oxygen-containing functional groups significantly simplify the access to functionalized graphene-based heterostructure NCs. [44-48]. This new material finds significant application in heterogeneous catalysis and support due to its tunable band gaps and effective intercalation of different compounds. By combining with semiconductor photocatalysts, GO and rGO can be used to create certain hetero structure composites with adjustable size and pore architectures, size distributions, and morphologies.

In this chapter, we discuss the recent development of research on the use of semiconductor NCs materials utilizing GO and rGO in the photocatalytic degradation of synthetic organic dye. In chronological sequence, the production method, characterisation, and photocatalytic activity of some representative samples as well as the mechanism of photocatalysis of those materials with regard to some Organic dye degradation are described. Additionally, we have attempted to identify the main obstacles and potential areas for further improving the photocatalytic activity for industrial applications of the graphene oxide based photocatalysts.

### **Synthesis of GO and rGO**

Jianguo Song et al [49] synthesized GO through the Hummer's method. In further specifics, 108 mL of H<sub>2</sub>SO<sub>4</sub> and 12 mL of H<sub>3</sub>PO<sub>4</sub> were combined with 5 g of graphite and 2.5 g of NaNO<sub>3</sub> and swirled in an ice bath for 10 min. 15 g of KMnO<sub>4</sub> were then gradually added so that the mixture's temperature stayed below 5°C. The suspension was then agitated for 60 minutes and reacted for 2 hours in an ice bath before being stirred once more for 60 minutes in a 40°C water bath. The mixture was heated to a steady 98°C for 60 minutes while water was continuously

added. Additional deionized water was added until the suspension had 400 mL in it. After 5 minutes, 15 mL of  $\text{H}_2\text{O}_2$  was added. The reaction by-product was centrifuged and repeatedly cleansed with DI water and 5% HCl solution. The product was then dried at  $60^\circ\text{C}$ . Anastasiia Kobylukh et al [50] synthesized GO through modified Hummer' method.

Ning Cao et al [45] synthesized GO and rGO through Hummer's method. In 400 mL of water, 400 mg of GO was dissolved using ultrasonication for 30 minutes. A uniform brown GO aqueous solution was produced as a result. By removing  $\text{NH}_3\text{H}_2\text{O}$ , the pH of the suspension was brought down to 10. The weight ratio of hydrazine hydrate and GO was maintained at 10: 7 after amounts of the compounds were added to suspension and heated at  $80^\circ\text{C}$  for 24 hours. Gradually, a kind of dark flocculent substance precipitated from the solution. Using high-quality filter paper, the product was obtained. The finished black product was then dried for 24 hours at  $80^\circ\text{C}$  after being cleaned with methanol and water. By heating GO in a vacuum chamber in an inert atmosphere, such as nitrogen, it is possible to reduce GO by thermal treatment while mostly preserving the hexagonal lattice structure of the carbon atoms. Combination or hybrid methods combine chemical and thermal reduction to achieve a greater degree of reduction, which leads to the transition into graphene to obtain a higher ratio of carbon to oxygen. Fig. 1 represents the schematic diagram for GO and rGO preparation.

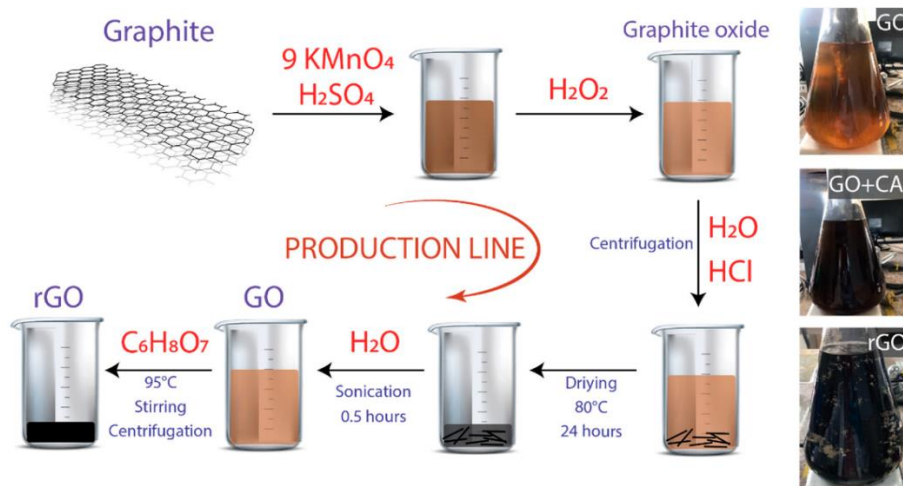


Fig. 1. Schematic diagram of GO and rGO preparation. (Ref.45)

## Properties of GO and rGO

Hydroxyl, carbonyl, epoxy and carboxyl functional groups are among the several oxygen functionalities found in GO [51,52]. By changing the oxygen functionality, it is possible to change the band gap of GO. Partially oxidized GO can serve as a semiconductor, but fully

oxidized GO can work as an electrical insulator. The UV-vis absorption spectra were used to calculate the band gap energy of GO, which was found to be 3.26 eV. GO has outstanding absorptivity and spatial charge separation are facilitated by the wide surface area, low density, efficient electron-transporting capability, good mechanical strength, distinctive electrical properties and high catalytic activity [53,54]. In order to improve photocatalytic activity, GO also functions as an excellent electron acceptor to increase photo-induced electron transfer [55].

rGO is superior to GO in terms of its strong features and potential applications, including better optical performance, increased electron mobility, higher conductivity, chemical stability, better adhesiveness, a larger surface area, superior thermal conductivity, and improved flexibility [56]. rGO can work well with metal oxides as a co-catalyst to improve photocatalytic redox capabilities under visible and UV light sources. It can also efficiently separate photo-generated electrons to surpass the rate of electron-hole recombination because of its greater electrical mobility. However, GO or rGO accelerates the photocatalytic degradation process due to their -interaction with organic dyes and the formation of hydrogen bonds amongst organic contaminants. Preventing EHPs recombination can increase the photodegradation efficiency of photocatalysts based on GO/rGO [57]. This can be done by doping with metal oxide nanoparticles (NPs), which can change the band gap of the materials. For instance, it has been discovered that the integration of rGO on metal oxide NPs improves photodegradation activity due to improved charge separation and enhanced active or reactive sites [58-61].

### **Metal oxides - GO NCs as photocatalyst**

When semiconducting metal oxide photocatalysts like ZnO, TiO<sub>2</sub>, V<sub>2</sub>O<sub>5</sub>, and many more absorb light, photocatalysis occurs. When electrons move from the lower energy valence band to the higher energy conduction band, electron-hole pairs are produced. Through migration, the newly formed electron-hole pairs start redox reactions with oxygen and water that break down the organic pollutants adsorbed on the surface of the photocatalyst. In order to increase the photodegradation efficiency GO was loaded on the metal oxide NPs. This might be explained by the fact that metal oxide-GO NCs have higher surface area that is active than GO alone. Additionally, GO sheets are capable of holding excited electrons from the metal oxide's conduction band to the valence band with ease. As a result, the metal oxide-GO NC has a greater energy gap between the conduction band and valence band, which inhibits electron-hole pair recombination [62,63].

Beaula Ruby Kamalam et al [63] synthesized  $V_2O_5$  nanorods (NRs) and  $V_2O_5$ -GO NCs by sonochemical process. GO was prepared by Hummer's method. To investigate the photodegradation of Victoria blue (VB) dye using the as-synthesized NRs and NCs under UV, visible and direct sunlight. A standard stock solution was prepared with a dye concentration of 10 mg in 1L (10 ppm). About 10 mg of GO-  $V_2O_5$  NCs was dispersed in 100 mL of VB dye solution. The bandgap for GO,  $V_2O_5$  NRs, and GO-  $V_2O_5$  NCs was estimated from the UV-Vis spectrum and is 2.2 eV, 2.22 eV, and 2.15 eV, respectively. GO-  $V_2O_5$  NCs are a viable option for visible-light driven photocatalysts due to their low bandgap energy. The photocatalytic degradation efficiency was maximum in  $V_2O_5$ -GO NCs under direct sunlight. The electrons in  $V_2O_5$  nanorods' valence band are stimulated to the conduction band and finally reached the go state during exposure to direct sunlight. The PL quenching for the GO-  $V_2O_5$  nanocomposite was found, which proved that electrons were effectively transported from the conduction band of  $V_2O_5$  to GO.  $V_2O_5$  nanorods recombine charge carriers at a slower rate because GO acts as an electron quencher since its relative energy level is close to the position of the conduction band of  $V_2O_5$ . In this way, GO advances the separation of charge carriers in  $V_2O_5$  and serves as a sink for photogenerated electrons. During the photodegradation process, these electron-hole pairs generate hydroxyl radicals ( $OH^\bullet$ ), superoxide radicals ( $O_2^\bullet^-$ ), and numerous other oxygenated reactive species. The degradation efficiency and the detailed photocatalytic mechanism is shown in Fig. 2.

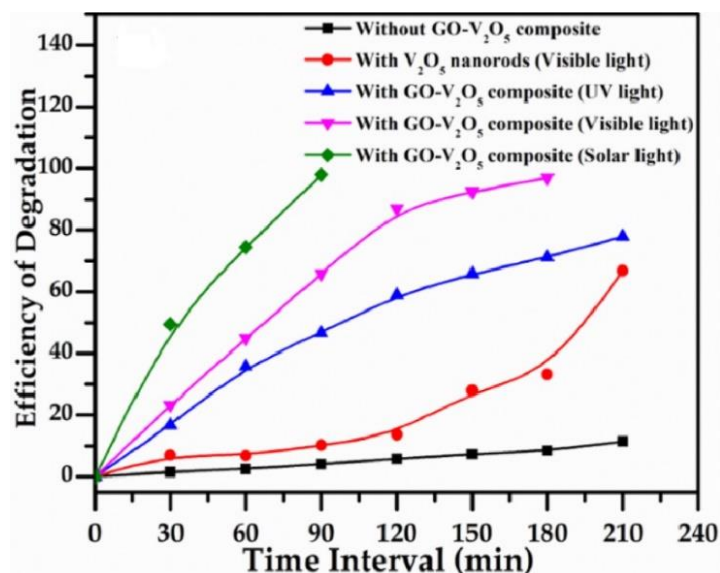


Fig. 2(a). Photocatalytic degradation efficiency graph of  $V_2O_5$  and  $V_2O_5$ -GO NCs under UV light and solar light (Ref.63)

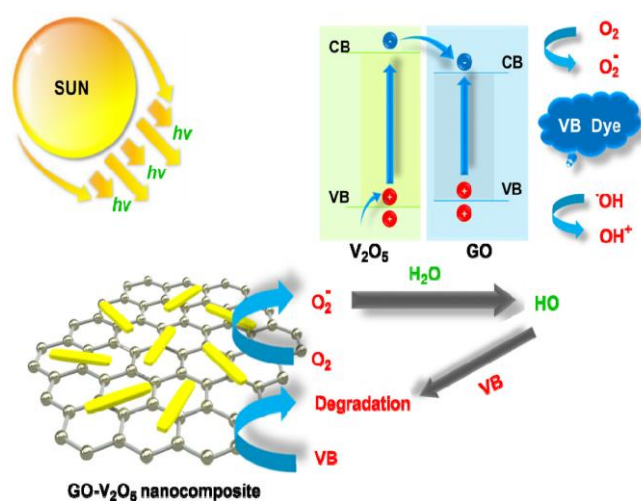


Fig. 2(b) Photocatalytic mechanism of  $V_2O_5$ -GO NCs (Ref.63)

Ahmar Umar et al [36] synthesized GO through Hummer's method and  $Fe_3O_4$ -GO through chemical precipitation method. Fig 3 (a-f) represents the morphological structure of the as-prepared  $Fe_3O_4$  NPs, GO, and  $Fe_3O_4$ -GO NCs. The nanoparticles are round and tightly packed due to high-density growth. Figure 3(c) depicts a typical TEM picture of  $Fe_3O_4$  nanoparticles, which verifies the spherical shape morphologies. The typical FESEM and TEM pictures of the generated  $Fe_3O_4$ -GO nanocomposite are shown in Figures 3(e) and (f), respectively. These images proved that the GO sheets are adorned with nanoparticles. The TEM image shown in Figure 3(f) shows that the  $Fe_3O_4$  nanoparticles are evenly distributed across the surface of the GO nanosheets. The average particle size was calculated from the TEM images was found to be in the range of  $11 \pm 2$  nm.

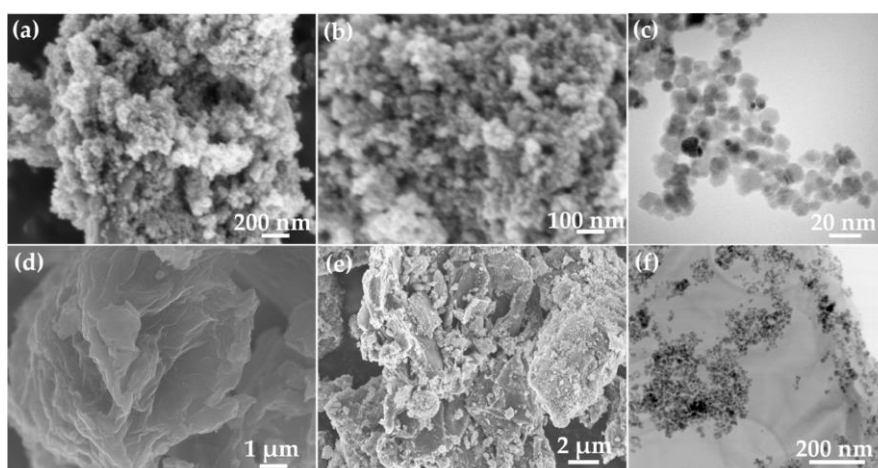


Fig. 3. (a, b) FESEM of  $Fe_3O_4$  NPs (c) TEM image of  $Fe_3O_4$  NPs, (d) FESEM of GO (e) FESEM of  $Fe_3O_4$ -GO NCs and (f) TEM images of  $Fe_3O_4$ -GO NCs. (Ref.36)

The energy band gap of GO was calculated using Tauc's plot from UV-Vis absorption spectrum and it was found to be 2.1 eV. After the addition of Fe<sub>3</sub>O<sub>4</sub> NPs on GO the bandgap was reduced to 1.59 eV. The photocatalytic degradation efficiencies of GO and Fe<sub>3</sub>O<sub>4</sub> - GO NCs towards Methylene blue (MB) under sunlight irradiation as shown in Fig. 4.

Photoirradiation excites the valence band electrons of the Fe<sub>3</sub>O<sub>4</sub> to the conduction band to reduce the molecular oxygen to superoxide ions. In the valence band, holes are created as a result of this, and when H<sub>2</sub>O is involved, the radicals OH are created. When the dye sample was continuously irradiated for 210 min, the degradation efficiency of GO towards MB dye was determined to be 75%. The greatest degrading efficiency of 91% for Fe<sub>3</sub>O<sub>4</sub>-GO, however, was seen after 30 minutes. This might be explained by Fe<sub>3</sub>O<sub>4</sub>-GO NCs having larger surface area that is active than GO. Additionally, EHP recombination is prevented in Fe<sub>3</sub>O<sub>4</sub>-GO NCs by the GO sheets, which also improve the energy difference between the conduction band and valence band in these materials. As a result, Fe<sub>3</sub>O<sub>4</sub>-GO NCs outperformed GO in terms of photocatalytic activity.

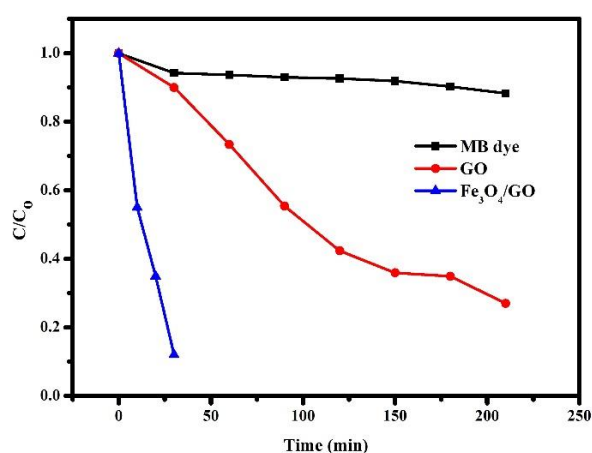


Fig. 4. Degradation efficiency of GO and Fe<sub>3</sub>O<sub>4</sub>-GO nanocomposites under sunlight  
(Ref.36)

Beaula Ruby Kamalam et al [64] synthesized nanocomposites were synthesized using sonication assisted simple solution mixing method by loading of  $\alpha$ -MoO<sub>3</sub> on GO sheets. GO was prepared through Hummer's method. TEM images revealed that the  $\alpha$ -MoO<sub>3</sub> NRs decorated on the GO sheets (Fig. 5 a-d). The band gap values of the graphene oxide,  $\alpha$ -MoO<sub>3</sub> and GO-MoO<sub>3</sub> were 2.4 eV, 3.0 eV and 2.96 eV respectively suggesting that the NCs are sensitive to visible regions of wavelength.



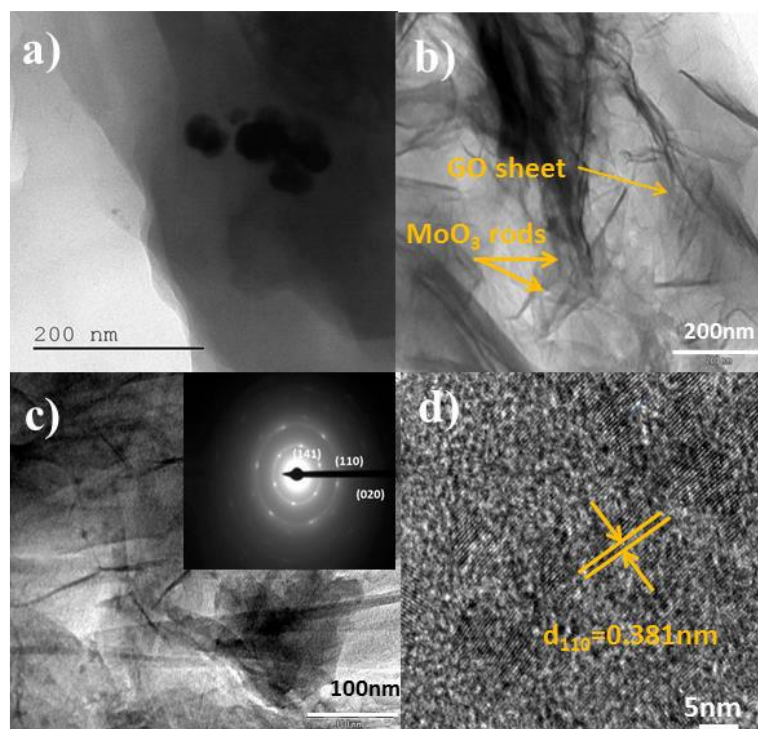


Fig.4 TEM images of (a) GO sheet (b) GO-MoO<sub>3</sub> (5 wt%) (c) GO-MoO<sub>3</sub> (10 wt %) (d) HRTEM images of GO-MoO<sub>3</sub> (5 wt%). Inset in c) SAED pattern of GO-MoO<sub>3</sub> (10 wt %).

(Ref.64)

Photocatalytic degradation efficiency of VB dye in the presence of as-synthesized NCs under visible light irradiation. The degradation efficiency of MoO<sub>3</sub> NRs was found to be 27% in 150 mins and GO-MoO<sub>3</sub> NCs was found to be 89% in 90 mins respectively (Fig. 5 a & b). The remarkable performance and enhanced absorptivity of the GO-MoO<sub>3</sub> nanocomposites are clearly responsible for the adsorption of dye molecules on the catalytic surface. The presence of graphene oxide may be the cause of the improvement in the speed of charge transportation and the separation of the charge carriers. As a result, the electrons produced by - MoO<sub>3</sub> are transported from graphene oxide's conduction band to molybdenum trioxide. Therefore, it is claimed that graphene oxide functions as an excellent electron acceptor in order to lower the recombination rate.

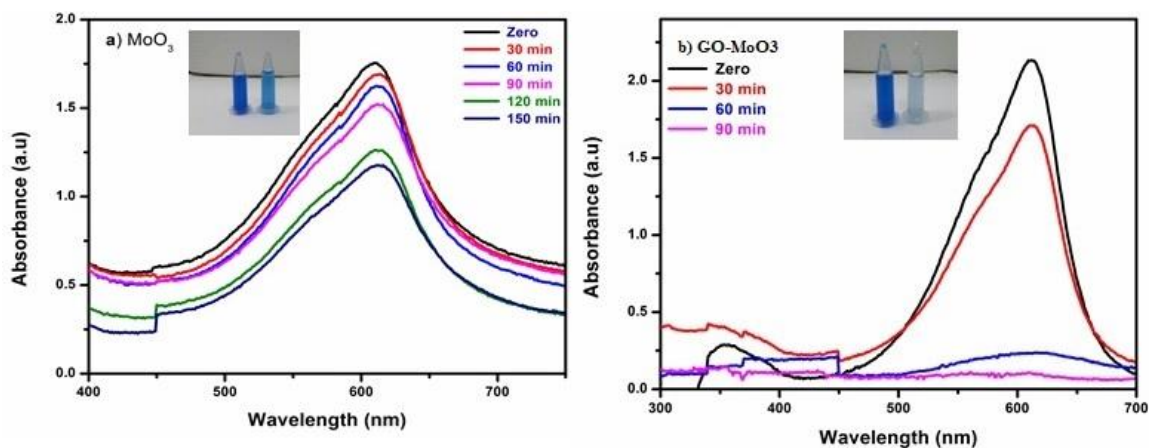


Fig. 5. Photocatalytic degradation VB dye under sunlight in the presence of (a)MoO<sub>3</sub> & (b) GO-MoO<sub>3</sub> (Ref.64)

Nathir. A. F., et al [27] synthesized GO-ZnO NCs embedded Ag and Cu NPs was synthesized through a simple one pot method. SEM images represent the massive volume of ZnO nanoparticles positioned over and between GO sheets (Fig. 6a) without any agglomeration. Fig. 6(b) and 6(c) shows the presence of Ag and Cu NPs on GO-ZnO NCs.

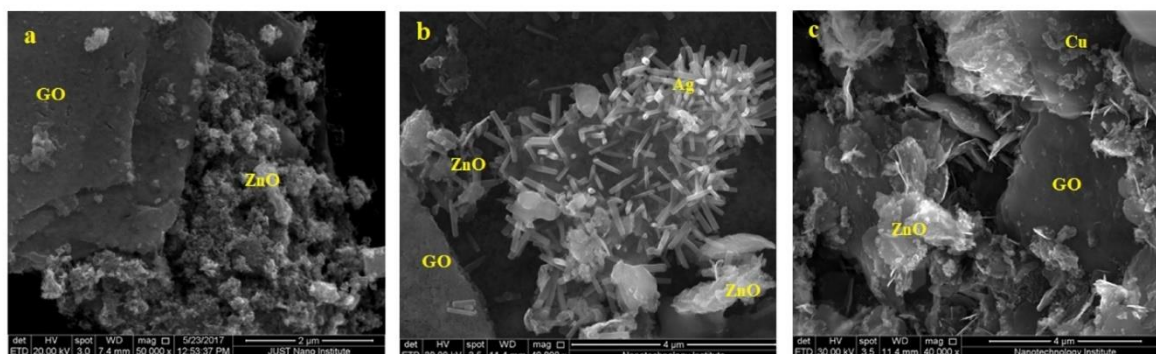


Fig. 6. SEM images of (a) GO-ZnO, (b) GO-ZnO-Ag, and (c) GO-ZnO-Cu (Ref.27)

The photodegradation efficiency of MB dye was examined in the presence of as-synthesized GO-ZnO, GO-ZnO-Ag, and GO-ZnO-Cu NCs under sunlight irradiation is represented in Fig. 7 (a-c). The degradation efficiency of GO-ZnO was found to be 84% in 90 mins. After the addition of Ag NPs, it was found to be 100% in 40 mins and Cu NPs it resulted to be 50% in 90mins. The inclusion of silver nanoparticles, which reduced the recombination of electron-hole pairs, and the influence of one-dimensional ZnO nanorods, which increased light-harvesting capacity and significantly increased the photoactivity of the catalyst, are credited with this unusual discovery. Ag nanoparticles' synergistic effect on the activity of ZnO through electron and hole trapping had an impact on the increase in hydroxyl radical generation. The

decrease in the degradation efficiency may be attributed to the electrical conductivity is higher in Ag than Cu NPs.

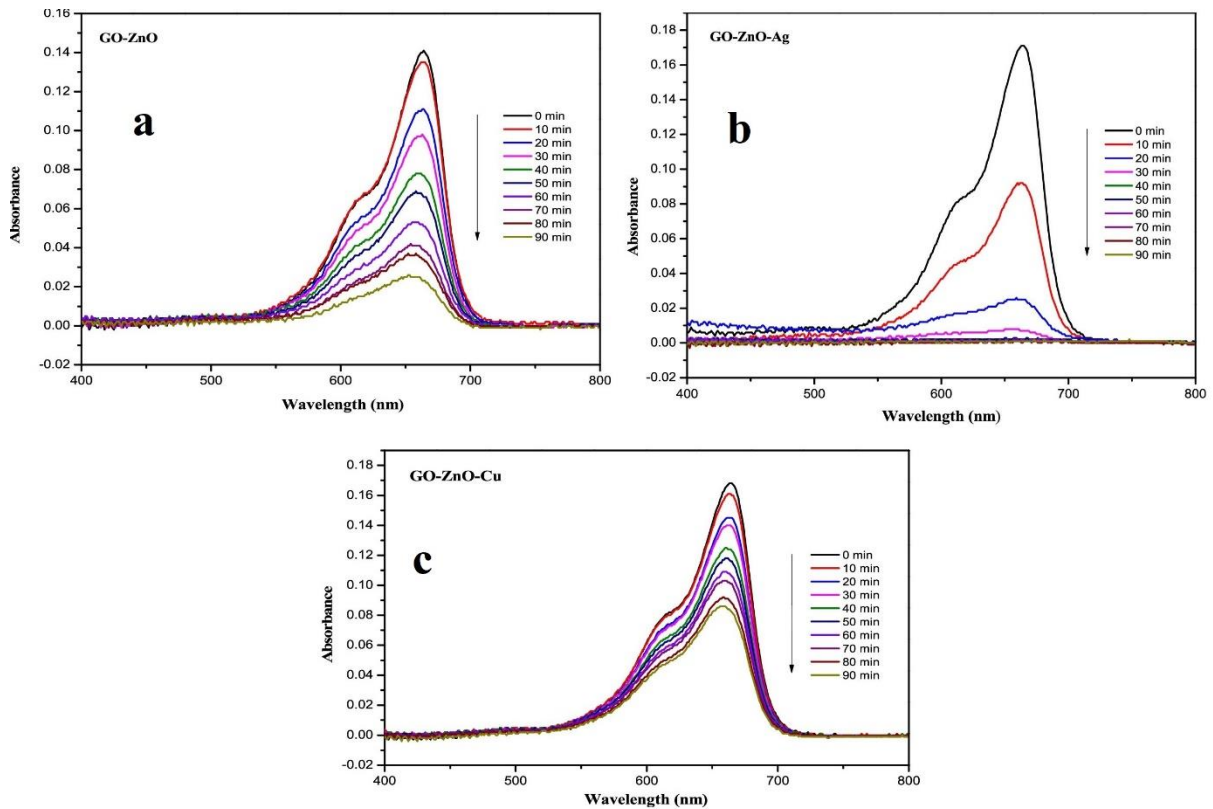


Fig. 7. Photocatalytic activity of (a)GO–ZnO, (b)GO–ZnO–Ag and (c)GO–ZnO–Cu NCs in degrading the MB dye (Ref.27)

### Metal oxides - rGO NCs as photocatalyst

In order to remove both organic and inorganic pollutants, carbon-based materials have typically been used in adsorption processes. Activated carbon is one of the most widely used adsorbents. The utilization of rGO for dye adsorption has recently increased. Due to various faults in the graphitic domains and the persistence of surficial oxygen functions, rGO is considered effective for the adsorptive removal of dyes. rGO often engages in interactions, electrostatic interactions, hydrophobic association, and structural conjugation with dyes. Numerous dyes can bind to rGO thanks to these interactions. rGO with a large surface area and high porosity are preferred in order to increase the adsorption capacity; this is possible by carefully monitoring the quality of the GO precursor and the reduction technique [65,66].

Siong et al [67] synthesized rGO at different reduction temperatures via an environmentally friendly solvothermal approach. By removing functionalities that are oxygenated from the surface, the rGO produced at 160°C clearly demonstrated the partial restoration of the sp<sup>2</sup> hybridization. Evaluations were made of the impacts of the initial dye concentration, catalyst

loading, light intensity, and solution pH. When 60 mg of catalyst, 50 ppm of dye at pH 11, and 60 W/m<sup>2</sup> of UV light source were utilized, it was shown that rGO-160 could produce a greater adsorptive removal (87.39%) and photocatalytic degradation (98.57%) of MB dye. After five consecutive cycles, there was no discernible decline in the MB photodegradation activity of rGO-160 (Fig. 8).

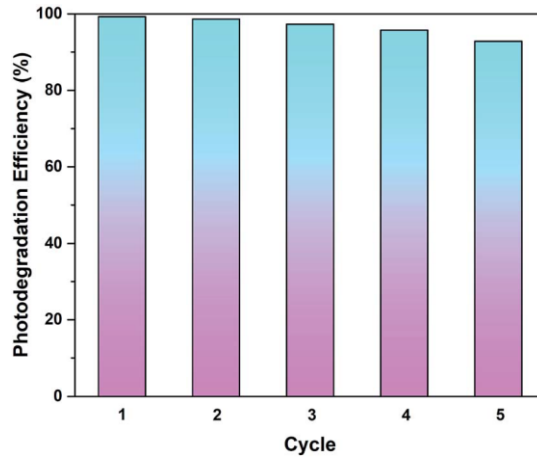


Fig. 8. Recyclability tests of rGO for MB dye degradation (Ref.68)

M. Jarvin et al [15] successfully synthesized Mn<sub>3</sub>O<sub>4</sub>-rGO NCs through a simple solvothermal method as shown in Fig. 9. The as-prepared NCs was used as a photocatalyst to degrade MB dye under sunlight. The pristine Mn<sub>3</sub>O<sub>4</sub> shows the efficiency of 34 % and the Mn<sub>3</sub>O<sub>4</sub>-rGO NC shows the efficiency of 60% at 120 mins. The band-band transition that caused the strong emission to be seen at 424 nm can be seen in the PL spectra of Mn<sub>3</sub>O<sub>4</sub> and Mn<sub>3</sub>O<sub>4</sub>-rGO NC. When compared to bare Mn<sub>3</sub>O<sub>4</sub>, the Mn<sub>3</sub>O<sub>4</sub>- rGO exhibits a peak intensity that is somewhat lower but still high. Due to edge defects in rGO, which cause a drop in peak intensity, excited electrons are trapped into the surface via typical flaws. This will reduce the recombination of electrons and holes, enhancing the photocatalytic activity of Mn<sub>3</sub>O<sub>4</sub>-rGO NC.



Fig. 9. Schematic illustration of the synthesis of Mn<sub>3</sub>O<sub>4</sub>-rGO NCs (Ref.15)

R. Fatima et al [47] synthesized transition metal oxides (TMO's) and their composite with rGO through facile co-precipitation method (Fig. 10). GO was prepared via Hummer's method.

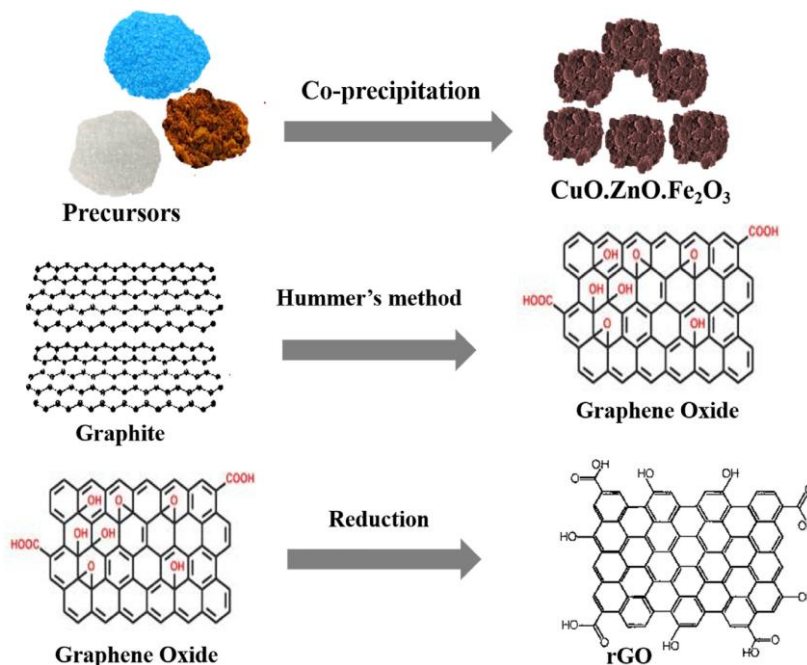


Fig. 10. Synthesis of mixed metal oxides  $\text{CuO.ZnO.Fe}_2\text{O}_3$ , GO and rGO (Ref.47)

The photogenerated electron is excited toward the photocatalyst's conduction band. By directing electrons toward the high energy level, the hybrid of different metal oxides and carbonaceous nanomaterials like GO, rGO, and CNTs can lessen the recombination of photogenerated electrons and holes. The oxygen molecules that were adsorbed on the photocatalyst's surface were converted into superoxide radicals ( $\text{O}_2^-$ ) and hydroxyl ions were transformed into OH oxidant radicals. The stacking properties of the carbonaceous materials rGO and CNTs make them an effective instrument for snatching electrons from the conduction band of mixed metal oxides and advancing redox reactions. In order to lessen photocorrosion, rGO provides an active site that postpones the recombination of photogenerated electrons and holes. Under UV irradiation, the  $\text{CuO.ZnO.Fe}_2\text{O}_3/\text{rGO}$  NCs exhibit the highest rate of MB dye degradation, 87%, in 90 minutes.

## **Conclusions**

From the above mentioned research reports it can be seen that photocatalytic degradation of organic pollutants, such as dyes and compounds that are toxic to humans and aquatic and terrestrial organisms as well as carcinogenic to humans, is crucial from both a human and environmental standpoint. Degradation by photocatalysis is an effective technique for getting rid of these harmful substances found in wastewater. pH value, catalyst dosage and temperature play a significant role in photocatalysis. Additionally, rGO has a superior conductivity behavior, which narrows the band gap to provide an intermediary energy level that encourages the PC to display its activity in the visible area and improves separation and reusability. It has also been discovered that external magnets may successfully separate nanocomposites having magnetic characteristics, such as rGO doped with iron nanoparticles or iron oxide. It may be possible for the current water treatment facilities and other water purification systems to use photo catalysis technology. When combined with other cutting-edge water treatment techniques like membrane technology, adsorption, etc., photo catalysis may provide synergistic benefits.

## References

1. Ahmad, Jahangir, and Kowsar Majid. "Enhanced visible light driven photocatalytic activity of CdO-graphene oxide heterostructures for the degradation of organic pollutants." *New Journal of Chemistry* 42, no. 5 (2018): 3246-3259.
2. Ajmal, A., I. Majeed, R. N. Malik, M. Iqbal, M. Arif Nadeem, I. Hussain, S. Yousaf, G. Mustafa, M. I. Zafar, and M. Amtiaz Nadeem. "Photocatalytic degradation of textile dyes on Cu<sub>2</sub>O-CuO/TiO<sub>2</sub> anatase powders." *Journal of environmental chemical engineering* 4, no. 2 (2016): 2138-2146.
3. Rahmani, Zahra, Majid Kermani, Mitra Gholami, Ahmad Jonidi Jafari, and Niyaz Mohammad Mahmoodi. "Effectiveness of photochemical and sonochemical processes in degradation of Basic Violet 16 (BV16) dye from aqueous solutions." *Iranian journal of environmental health science & engineering* 9, no. 1 (2012): 1-7.
4. Madiha, B., Q. Zahid, M. Nida, and S. S. Abdul. "Studie on Malachite Green Dye Degradation by Biogenic Metal Nano Cuo And Cuo/Zno Nano Composites. Arch Nano Op Acc J 1 (4). 2018." ANOAJ. MS. ID 119.
5. Taourati, Rabab, Mohamed Khaddor, Ali Laghzal, and Achraf El Kasmi. "Facile one-step synthesis of highly efficient single oxide nanoparticles for photocatalytic application." *Scientific African* 8 (2020): e00305.
6. Bhattacharya, Debopriya, Debopriyo Ghoshal, Dheeraj Mondal, Biplab Kumar Paul, Navonil Bose, Sukhen Das, and Mousumi Basu. "Visible light driven degradation of brilliant green dye using titanium based ternary metal oxide photocatalyst." *Results in Physics* 12 (2019): 1850-1858.
7. Garg, V. K., Rakesh Kumar, and Renuka Gupta. "Removal of malachite green dye from aqueous solution by adsorption using agro-industry waste: a case study of *Prosopis cineraria*." *Dyes and pigments* 62, no. 1 (2004): 1-10.
8. Raval, Nirav P., Prapti U. Shah, and Nisha K. Shah. "Malachite green "a cationic dye" and its removal from aqueous solution by adsorption." *Applied Water Science* 7, no. 7 (2017): 3407-3445.
9. Moumeni, Ouarda, Oualid Hamdaoui, and Christian Pétrier. "Sonochemical degradation of malachite green in water." *Chemical Engineering and Processing: Process Intensification* 62 (2012): 47-53.
10. Berberidou, C. P. I. X., I. Poulios, N. P. Xekoukoulotakis, and D. Mantzavinos. "Sonolytic, photocatalytic and sonophotocatalytic degradation of malachite green in aqueous solutions." *Applied Catalysis B: Environmental* 74, no. 1-2 (2007): 63-72.

11. Behnajady, Mohammad A., Nasser Modirshahla, Mohammad Shokri, and Behrouz Vahid. "Effect of operational parameters on degradation of Malachite Green by ultrasonic irradiation." *Ultrasonics Sonochemistry* 15, no. 6 (2008): 1009-1014.
12. Khattri, S. D., and M. K. Singh. "Removal of malachite green from dye wastewater using neem sawdust by adsorption." *Journal of hazardous materials* 167, no. 1-3 (2009): 1089-1094.
13. Mageshwari, K., et al. "Template-free synthesis of MgO nanoparticles for effective photocatalytic applications." *Powder technology* 249 (2013): 456-462.
14. Kumar, S. Ashok, M. Jarvin, S. S. R. Inbanathan, Ahmad Umar, N. P. Lalla, Nelson Y. Dzade, Hassan Algadi, Qazi Inamur Rahman, and Sotirios Baskoutas. "Facile green synthesis of magnesium oxide nanoparticles using tea (*Camellia sinensis*) extract for efficient photocatalytic degradation of methylene blue dye." *Environmental Technology & Innovation* 28 (2022): 102746.
15. Jarvin, M., S. Ashok Kumar, G. Vinodhkumar, E. Manikandan, and S. S. R. Inbanathan. "Enhanced photocatalytic performance of Hausmannite Mn<sub>3</sub>O<sub>4</sub>-rGO nanocomposite in degrading methylene blue." *Materials Letters* 305 (2021): 130750.
16. Hong, Xiaodong, Xu Wang, Yang Li, Jiawei Fu, and Bing Liang. "Progress in graphene/metal oxide composite photocatalysts for degradation of organic pollutants." *Catalysts* 10, no. 8 (2020): 921.
17. Silvestri, Siara, Juliane Facco de Oliveira, and Edson Luiz Foletto. "Degradation of methylene blue using Zn<sub>2</sub>SnO<sub>4</sub> catalysts prepared with pore-forming agents." *Materials Research Bulletin* 117 (2019): 56-62.
18. Aftab, Saima, Tayyaba Shabir, Afzal Shah, Jan Nisar, Iltaf Shah, Haji Muhammad, and Noor S. Shah. "Highly efficient visible light active doped ZnO photocatalysts for the treatment of wastewater contaminated with dyes and pathogens of emerging concern." *Nanomaterials* 12, no. 3 (2022): 486.
19. Ravishankar, T. N., K. Manjunatha, T. Ramakrishnappa, G. Nagaraju, Dhanith Kumar, S. Sarakar, B. S. Anandakumar, G. T. Chandrappa, Viswanath Reddy, and J. Dupont. "Comparison of the photocatalytic degradation of trypan blue by undoped and silver-doped zinc oxide nanoparticles." *Materials science in semiconductor processing* 26 (2014): 7-17.
20. Ravishankar, T. N., K. Manjunatha, T. Ramakrishnappa, G. Nagaraju, Dhanith Kumar, S. Sarakar, B. S. Anandakumar, G. T. Chandrappa, Viswanath Reddy, and J. Dupont. "Comparison of the photocatalytic degradation of trypan blue by undoped and silver-doped zinc oxide nanoparticles." *Materials science in semiconductor processing* 26 (2014): 7-17.



21. Wang, Ronghua, John Haozhong Xin, Yang Yang, Hongfang Liu, Liming Xu, and Junhui Hu. "The characteristics and photocatalytic activities of silver doped ZnO nanocrystallites." *Applied Surface Science* 227, no. 1-4 (2004): 312-317.
22. Elangovan, S. V., N. Sivakumar, and V. Chandramohan. "Magnesium doped zinc oxide nanocrystals for photo-catalytic applications." *Journal of Materials Science: Materials in Electronics* 26, no. 11 (2015): 8753-8759.
23. Etacheri, Vinodkumar, Roshith Roshan, and Vishwanathan Kumar. "Mg-doped ZnO nanoparticles for efficient sunlight-driven photocatalysis." *ACS applied materials & interfaces* 4, no. 5 (2012): 2717-2725.
24. Sangpour, Parvaneh, Fatemeh Hashemi, and Alireza Z. Moshfegh. "Photoenhanced degradation of methylene blue on cosputtered M: TiO<sub>2</sub> (M= Au, Ag, Cu) nanocomposite systems: a comparative study." *The Journal of Physical Chemistry C* 114, no. 33 (2010): 13955-13961.
25. Mandal, Soumen, Srinivas Mallapur, Madhusudana Reddy, Jitendra Kumar Singh, Dong-Eun Lee, and Taejoon Park. "An overview on graphene-metal oxide semiconductor nanocomposite: A promising platform for visible light photocatalytic activity for the treatment of various pollutants in aqueous medium." *Molecules* 25, no. 22 (2020): 5380.
26. El-Shafai, Nagi M., Mohamed E. El-Khouly, Maged El-Kemary, Mohamed S. Ramadan, and Mamdouh S. Masoud. "Graphene oxide–metal oxide nanocomposites: fabrication, characterization and removal of cationic rhodamine B dye." *RSC advances* 8, no. 24 (2018): 13323-13332.
27. Al-Rawashdeh, Nathir AF, Odai Allabadi, and Mohannad T. Aljarrah. "Photocatalytic activity of graphene oxide/zinc oxide nanocomposites with embedded metal nanoparticles for the degradation of organic dyes." *ACS omega* 5, no. 43 (2020): 28046-28055.
28. Atchudan, Raji, Thomas Nesakumar Jebakumar Immanuel Edison, Suguna Perumal, Dhanapalan Karthikeyan, and Yong Rok Lee. "Facile synthesis of zinc oxide nanoparticles decorated graphene oxide composite via simple solvothermal route and their photocatalytic activity on methylene blue degradation." *Journal of Photochemistry and Photobiology B: Biology* 162 (2016): 500-510.
29. Ranjan, Pranay, Jayakumar Balakrishnan, and Ajay D. Thakur. "Dye adsorption behavior of graphene oxide." *Materials Today: Proceedings* 11 (2019): 833-836.
30. Durmus, Zehra, Belma Zengin Kurt, and Ali Durmus. "Synthesis and characterization of graphene oxide/zinc oxide (GO/ZnO) nanocomposite and its utilization for photocatalytic degradation of basic fuchsin dye." *ChemistrySelect* 4, no. 1 (2019): 271-278.

31. Kamalam, M. Beaula Ruby, S. S. R. Inbanathan, B. Renganathan, and K. Sethuraman. "Enhanced sensing of ethanol gas using fiber optics sensor by hydrothermally synthesized GO-WO<sub>3</sub> nanocomposites." *Materials Science and Engineering: B* 263 (2021): 114843.
32. Zubir, Nor Aida, Christelle Yacou, Xiwang Zhang, and João C. Diniz da Costa. "Optimisation of graphene oxide–iron oxide nanocomposite in heterogeneous Fenton-like oxidation of Acid Orange 7." *Journal of environmental chemical engineering* 2, no. 3 (2014): 1881-1888.
33. Raliya, Ramesh, Caroline Avery, Sampa Chakrabarti, and Pratim Biswas. "Photocatalytic degradation of methyl orange dye by pristine titanium dioxide, zinc oxide, and graphene oxide nanostructures and their composites under visible light irradiation." *Applied Nanoscience* 7, no. 5 (2017): 253-259.
34. Mura, Stefania, Yu Jiang, Irene Vassalini, Alessandra Gianoncelli, Ivano Alessandri, Gaetano Granozzi, Laura Calvillo et al. "Graphene oxide/iron oxide nanocomposites for water remediation." *ACS Applied Nano Materials* 1, no. 12 (2018): 6724-6732.
35. Sivaraj, Durairaj, Kalimuthu Vijayalakshmi, Manickam Srinivasan, and Perumalsamy Ramasamy. "Graphene oxide reinforced bismuth titanate for photocatalytic degradation of azo dye (DB15) prepared by hydrothermal method." *Ceramics International* 47, no. 17 (2021): 25074-25080.
36. Umar, Ahmad, S. Ashok Kumar, S. S. R. Inbanathan, Maryam Modarres, Rajesh Kumar, Hassan Algadi, Ahmed A. Ibrahim et al. "Enhanced sunlight-driven photocatalytic, supercapacitor and antibacterial applications based on graphene oxide and magnetite-graphene oxide nanocomposites." *Ceramics International* (2022).
37. Ikram, M., T. Inayat, A. Haider, A. Ul-Hamid, J. Haider, W. Nabgan, A. Saeed et al. "Graphene oxide-doped MgO nanostructures for highly efficient dye degradation and bactericidal action." *Nanoscale research letters* 16, no. 1 (2021): 1-11.
38. Saroyan, Hayarpi, George Z. Kyzas, and Eleni A. Deliyanni. "Effective dye degradation by graphene oxide supported manganese oxide." *Processes* 7, no. 1 (2019): 40.
39. Zhang, Junye, Enjie Ding, Shicai Xu, Zhenhua Li, Ali Fakhri, and Vinod Kumar Gupta. "Production of metal oxides nanoparticles based on poly-alanine/chitosan/reduced graphene oxide for photocatalysis degradation, anti-pathogenic bacterial and antioxidant studies." *International Journal of Biological Macromolecules* 164 (2020): 1584-1591.
40. Khan, Ziyauddin, Tridip Ranjan Chetia, Anil Kumar Vardhaman, Dipankar Barpuzary, Chivukula V. Sastri, and Mohammad Qureshi. "Visible light assisted photocatalytic

- hydrogen generation and organic dye degradation by CdS–metal oxide hybrids in presence of graphene oxide." *RSC advances* 2, no. 32 (2012): 12122-12128.
41. Lin, Yi, Ruoyu Hong, Huaiyin Chen, Di Zhang, and Jinjia Xu. "Green synthesis of ZnO-GO composites for the photocatalytic degradation of methylene blue." *Journal of Nanomaterials* 2020 (2020).
  42. El-Shafai, Nagi M., Mohamed E. El-Khouly, Maged El-Kemary, Mohamed S. Ramadan, and Mamdouh S. Masoud. "Graphene oxide–metal oxide nanocomposites: fabrication, characterization and removal of cationic rhodamine B dye." *RSC advances* 8, no. 24 (2018): 13323-13332.
  43. Rehman, Attiya, Aysha Daud, Muhammad Farooq Warsi, Imran Shakir, Philips O. Agboola, Muhammad Ilyas Sarwar, and Sonia Zulfiqar. "Nanostructured maghemite and magnetite and their nanocomposites with graphene oxide for photocatalytic degradation of methylene blue." *Materials Chemistry and Physics* 256 (2020): 123752.
  44. Khan, Faisal, Mohd Shoeb Khan, Shahid Kamal, Mohammad Arshad, Syed Ishraque Ahmad, and Shahab AA Nami. "Recent advances in graphene oxide and reduced graphene oxide based nanocomposites for the photodegradation of dyes." *Journal of Materials Chemistry C* 8, no. 45 (2020): 15940-15955.
  45. Cao, Ning, and Yuan Zhang. "Study of reduced graphene oxide preparation by Hummers' method and related characterization." *Journal of Nanomaterials* 2015 (2015).
  46. Abdolhosseinzadeh, Sina, Hamed Asgharzadeh, and Hyoung Seop Kim. "Fast and fully-scalable synthesis of reduced graphene oxide." *Scientific reports* 5, no. 1 (2015): 1-7.
  47. Fatima, Rukia, Muhammad Farooq Warsi, Sonia Zulfiqar, Sameh A. Ragab, Imran Shakir, and Muhammad Ilyas Sarwar. "Nanocrystalline transition metal oxides and their composites with reduced graphene oxide and carbon nanotubes for photocatalytic applications." *Ceramics International* 46, no. 10 (2020): 16480-16492.
  48. Tene, Talia, Gabriela Tubon Usca, Marco Guevara, Raul Molina, Francesco Veltri, Melvin Arias, Lorenzo S. Caputi, and Cristian Vacacela Gomez. "Toward large-scale production of oxidized graphene." *Nanomaterials* 10, no. 2 (2020): 279.
  49. Song, Jianguo, Xinzhi Wang, and Chang-Tang Chang. "Preparation and characterization of graphene oxide." *Journal of Nanomaterials* 2014 (2014).
  50. Kobyliukh, Anastasiia, Karolina Olszowska, Marcin Godzierz, Aleksandra Kordyka, Jerzy Kubacki, Yevgen Mamunya, Sławomira Pusz, Ivanka Stoycheva, and Urszula Szeluga. "Effect of graphene material structure and iron oxides deposition method on morphology

- and properties of graphene/iron oxide hybrids." *Applied Surface Science* 573 (2022): 151567.
51. Brisebois, P. P., and Mohamed Siaj. "Harvesting graphene oxide—years 1859 to 2019: a review of its structure, synthesis, properties and exfoliation." *Journal of Materials Chemistry C* 8, no. 5 (2020): 1517-1547.
  52. Singh, Nirbhai, Sk Riyajuddin, Kaushik Ghosh, Surinder K. Mehta, and Abhijit Dan. "Chitosan-graphene oxide hydrogels with embedded magnetic iron oxide nanoparticles for dye removal." *ACS Applied Nano Materials* 2, no. 11 (2019): 7379-7392.
  53. Chen, Da, Hongbin Feng, and Jinghong Li. "Graphene oxide: preparation, functionalization, and electrochemical applications." *Chemical reviews* 112, no. 11 (2012): 6027-6053.
  54. Al Kausor, Mehdi, and Dhruva Chakraborty. "Graphene oxide based semiconductor photocatalysts for degradation of organic dye in waste water: a review on fabrication, performance enhancement and challenges." *Inorganic Chemistry Communications* 129 (2021): 108630.
  55. Jamjoum, Hayfa Alajilani Abraheem, Khalid Umar, Rohana Adnan, Mohd R. Razali, and Mohamad Nasir Mohamad Ibrahim. "Synthesis, characterization, and photocatalytic activities of graphene oxide/metal oxides nanocomposites: A review." *Frontiers in Chemistry* 9 (2021).
  56. Nada, Amr A., Hesham R. Tantawy, Mohamed A. Elsayed, Mikhael Bechelany, and Mohamed E. Elmowafy. "Elaboration of nano titania-magnetic reduced graphene oxide for degradation of tartrazine dye in aqueous solution." *Solid State Sciences* 78 (2018): 116-125.
  57. Fatima, Rukia, Muhammad Farooq Warsi, Muhammad Ilyas Sarwar, Imran Shakir, Philips O. Agboola, Mohamed F. Aly Aboud, and Sonia Zulfiqar. "Synthesis and characterization of hetero-metallic oxides-reduced graphene oxide nanocomposites for photocatalytic applications." *Ceramics International* 47, no. 6 (2021): 7642-7652.
  58. Benjwal, Poonam, Manish Kumar, Pankaj Chamoli, and Kamal K. Kar. "Enhanced photocatalytic degradation of methylene blue and adsorption of arsenic (iii) by reduced graphene oxide (rGO)—metal oxide (TiO<sub>2</sub>/Fe<sub>3</sub>O<sub>4</sub>) based nanocomposites." *Rsc Advances* 5, no. 89 (2015): 73249-73260.
  59. Zhang, Jintao, Zhigang Xiong, and X. S. Zhao. "Graphene—metal—oxide composites for the degradation of dyes under visible light irradiation." *Journal of Materials Chemistry* 21, no. 11 (2011): 3634-3640.

60. Raghavan, Nivea, Sakthivel Thangavel, and Gunasekaran Venugopal. "Enhanced photocatalytic degradation of methylene blue by reduced graphene-oxide/titanium dioxide/zinc oxide ternary nanocomposites." *Materials Science in Semiconductor Processing* 30 (2015): 321-329.
61. Ramesh, K., B. Gnanavel, and Mohd Shkir. "Enhanced visible light photocatalytic degradation of bisphenol A (BPA) by reduced graphene oxide (RGO)–metal oxide (TiO<sub>2</sub>, ZnO and WO<sub>3</sub>) based nanocomposites." *Diamond and Related Materials* 118 (2021): 108514.
62. Khurshid, Farheen, M. Jeyavelan, and S. Nagarajan. "Photocatalytic dye degradation by graphene oxide doped transition metal catalysts." *Synthetic Metals* 278 (2021): 116832.
63. Kamalam, M. Beaula Ruby, S. S. R. Inbanathan, K. Sethuraman, Ahmad Umar, Hassan Algadi, Ahmed A. Ibrahim, Qazi Inamur Rahman, Christos S. Garoufalidis, and Sotirios Baskoutas. "Direct sunlight-driven enhanced photocatalytic performance of V<sub>2</sub>O<sub>5</sub> nanorods/graphene oxide nanocomposites for the degradation of Victoria blue dye." *Environmental Research* 199 (2021): 111369.
64. Kamalam, M. Beaula Ruby, S. S. R. Inbanathan, and K. Sethuraman. "Enhanced photocatalytic activity of graphene oxide/MoO<sub>3</sub> nanocomposites in the degradation of Victoria Blue Dye under visible light irradiation." *Applied Surface Science* 449 (2018): 685-696.
65. Aragaw, Belete Asefa, and Atsedemariam Dagnaw. "Copper/reduced graphene oxide nanocomposite for high performance photocatalytic methylene blue dye degradation." *Ethiopian Journal of Science and Technology* 12, no. 2 (2019): 125-137.
66. Liu, Sen, Jingqi Tian, Lei Wang, Yonglan Luo, and Xuping Sun. "One-pot synthesis of CuO nanoflower-decorated reduced graphene oxide and its application to photocatalytic degradation of dyes." *Catalysis Science & Technology* 2, no. 2 (2012): 339-344.
67. Siong, Valerie Ling Er, Kian Mun Lee, Joon Ching Juan, Chin Wei Lai, Xin Hong Tai, and Cheng Seong Khe. "Removal of methylene blue dye by solvothermally reduced graphene oxide: a metal-free adsorption and photodegradation method." *RSC advances* 9, no. 64 (2019): 37686-37695.